

Vortex loops entry into type-II superconductors

A. V. Samokhvalov

*Institute for physics of microstructures
Russian Academy of Sciences
603600, Nizhny Novgorod, Russia
e-mail: samokh@ipm.sci-nnov.ru*

ABSTRACT

The magnetic field distribution, the magnetic flux, and the free energy of an Abrikosov vortex loop near a flat surface of type-II superconductors are calculated in the London approximation. The shape of such a vortex line is a semicircle of arbitrary radius. The interaction of the vortex half-ring and an external homogeneous magnetic field applied along the surface is studied. The magnitude of the energy barrier against the vortex expansion into superconductor is found. The possibilities of formation of an equilibrium vortex line determined by the structure of the applied magnetic field by creating the expanding vortex loops near the surface of type-II superconductor are discussed.

1. INTRODUCTION

In a mixed state a magnetic field penetrates into type-II superconductors (SC) in the form of Abrikosov vortices having one quantum of magnetic flux $\Phi_0 = \pi\hbar c/e$ [1]. The presence of these vortices in SC and their interaction with inhomogeneities and defects of the material (pinning) determine both the magnetic properties of SC [2] and the ability of SC to carry a current without a resistance [3]. In the vortex core, where the magnetic field achieves its maximum, superconductivity is destroyed and the order parameter describing the superconducting properties of the material vanishes. The center of the vortex core defines the location of the vortex line (VL). The equilibrium form of the vortex lines in type-II superconductors reproduce the structure of an applied magnetic field. Thus, the homogeneous magnetic field generates a two-dimensional lattice of rectilinear vortex lines

directed along the field. The vortex penetration in SC is delayed significantly due to the presence of the surface Bean–Livingston (BL) barrier [4, 5]. An increase of an applied magnetic field H_0 results in a decrease of the BL barrier. The barrier is destroyed, then the field H_0 reaches the thermodynamic critical field H_{cm} . If the applied magnetic field $H_0 < H_{cm}$, the penetration of vortices in SC occurs as a result of sufficiently large fluctuations. In this case the vortex line produced near the surface forms a semicircle (vortex loop) the ends of which touch the superconductor surface [6, 7, 8]. A minimal critical size of the loop exists so that the vortex does not collapse at the surface but expands into the SC.

In this paper we consider the conditions of formation of the vortex loops near a flat surface of a type–II superconductor in the applied magnetic field parallel to the surface. In section 2, the magnetic field, the magnetic flux and the free energy of the solitary Abrikosov vortex in the form of a semicircle of arbitrary radius are calculated in the London approach. In section 3, the interaction of the vortex half–ring and an applied homogeneous magnetic field is studied. In this section we calculate the Gibbs free energy and determine the energy barrier preventing creation of expanding vortex loops. In section 4 the processes of formation of equilibrium VLs, defined by the applied magnetic field are discussed. The development of a rectilinear VL parallel to the applied magnetic field by intersection and cross joining of adjacent vortex loops is considered.

2. VORTEX HALF–RING NEAR THE SURFACE OF A SUPERCONDUCTOR

Let us consider a type–II superconductor occupying the region $z \leq 0$ and bounded by the surface S coincident with the coordinate plane (xy) . We assume that the vortex line is a semicircle of arbitrary radius ρ_v lying in the plane (yz) parallel to the applied magnetic field $\mathbf{H}_0$ (fig. 1). Due to the continuity of the magnetic flux, the end points of the VL have to be placed at the surface S [6]. The London approach is appropriate for extreme type–II superconductors with a large Ginzburg–Landau parameter $\kappa = \lambda/\xi \gg 1$, where λ is the magnetic field penetration depth and ξ is the coherence length. In the London model the magnetic field distribution $\mathbf{H}$ in SC ($z \leq 0$) is described by the London equation [9]:

$$\mathbf{H} + \text{rot rot } \mathbf{H} = \mathbf{e}_v \delta(\mathbf{r} - \mathbf{r}_v). \quad (1)$$

Here $\mathbf{r}_v$ is the radius vector defining the VL location in space, and $\mathbf{e}_v$ is the unit vector directed along the VL. Outside the superconductor ($z > 0$) there are no currents, and the magnetic field $\mathbf{H}_s$, produced by the flux line, is yielded by the Maxwell equations:

$$\text{rot } \mathbf{H}_s = 0, \quad \text{div } \mathbf{H}_s = 0. \quad (2)$$

The boundary conditions for the surface S can be obtained from the continuity of all components of the magnetic field in the plane $z = 0$:

$$\mathbf{H} = \mathbf{H}_s. \quad (3)$$

Everywhere here we use dimensionless units and assume that the magnetic flux Φ and the coordinate vector $\mathbf{r}$ are scaled by the flux quantum Φ_0 and the magnetic field penetration depth λ , respectively. For these units the scale of the magnetic field is Φ_0/λ^2 , and the current density j is measured by the units of $c\Phi_0/\lambda^3$.

Due to the linearity of equation (1) and boundary conditions (3) we represent the magnetic field $\mathbf{H}$ in the SC as a superposition:

$$\mathbf{H} = \mathbf{H}_v + \mathbf{H}_d. \quad (4)$$

The term $\mathbf{H}_v = H_v \mathbf{e}_v$ describes the structure of the magnetic field of a toroidal Abrikosov vortex with a VL consisting of a circle of radius ρ_v . In the cylindrical coordinate system $(\rho = \sqrt{y^2 + z^2}, \varphi, x)$ the component $H_v(\rho, x)$ satisfies the equation [10]:

$$\frac{\partial^2 H_v}{\partial \rho^2} + \frac{1}{\rho} \frac{\partial H_v}{\partial \rho} + \frac{\partial^2 H_v}{\partial x^2} - \left(1 + \frac{1}{\rho^2}\right) H_v = -\delta(\rho - \rho_v) \delta(x). \quad (5)$$

The solution of equation (5) for arbitrary vortex radius ρ_v , was obtained in [10, 11, 12] by means of the Fourier–Bessel transform, and can be represented as follows:

$$H_v(\rho, x) = \frac{\rho_v}{2\pi} \int_{-\infty}^{+\infty} dq \exp(iqx) \begin{cases} I_1(\rho\sqrt{1+q^2})K_1(\rho_v\sqrt{1+q^2}), & \rho \leq \rho_v; \\ I_1(\rho_v\sqrt{1+q^2})K_1(\rho\sqrt{1+q^2}), & \rho \geq \rho_v, \end{cases} \quad (6)$$

where $I_1(\zeta)$, $K_1(\zeta)$ are the modified Bessel functions of the first and second kind. The term $\mathbf{H}_d$ is the solution of the homogeneous London equation

$$\mathbf{H}_d + \text{rot rot } \mathbf{H}_d = 0 \quad (7)$$

in the half-space $z \leq 0$ with the boundary condition (3). To solve equation (7) it is convenient to represent the components $\mathbf{H}_d = (H_d^x, H_d^y, H_d^z)$ in the form of the two dimensional Fourier transform over spatial harmonics:

$$H_d^\alpha = \frac{1}{2\pi} \int_{-\infty}^{+\infty} dq \exp(iqx) \int_{-\infty}^{+\infty} du \exp(iuy) C_d^\alpha(q, u) \exp(z\sqrt{1+q^2+u^2}), \quad (8)$$

$\alpha = x, y, z.$

Equation (7) then reduces to the simple algebraic relation for the coefficients $C_d^\alpha(q, u)$:

$$-q C_d^x - u C_d^y + i\sqrt{1+q^2+u^2} C_d^z = 0. \quad (9)$$

In compliance with (2), the magnetic field $\mathbf{H}_s$ can be written as a negative gradient of a scalar potential U_s :

$$\mathbf{H}_s = -\nabla U_s, \quad (10)$$

and the potential U_s obeys Laplace's equation

$$\Delta U_s = 0. \quad (11)$$

It is evident, that the solution of equation (11) can be represented in the form:

$$U_s = \frac{1}{2\pi} \int_{-\infty}^{+\infty} dq \exp(iqx) \int_{-\infty}^{+\infty} du \exp(iuy) C_s(q, u) \exp(-z\sqrt{q^2 + u^2}). \quad (12)$$

The boundary conditions for the magnetic field (3) lead to three algebraic equations for the so far undetermined coefficients $C_d^\alpha(q, u)$, $C_s(q, u)$:

$$C_d^x = -i q C_s, \quad C_d^y = -i u C_s, \quad C_d^z - \frac{i}{\pi} S_v(q, u) = \sqrt{q^2 + u^2} C_s. \quad (13)$$

The solutions of the linear algebraic system (9,13) for $q^2 + u^2 \neq 0$ are

$$\begin{aligned} C_d^x &= -\frac{q\sqrt{1+q^2+u^2} S_v(q, u)}{\pi\sqrt{q^2+u^2} \left(\sqrt{1+q^2+u^2} + \sqrt{q^2+u^2}\right)}, \\ C_d^y &= -\frac{u\sqrt{1+q^2+u^2} S_v(q, u)}{\pi\sqrt{q^2+u^2} \left(\sqrt{1+q^2+u^2} + \sqrt{q^2+u^2}\right)}, \\ C_d^z &= \frac{i\sqrt{q^2+u^2} S_v(q, u)}{\pi \left(\sqrt{1+q^2+u^2} + \sqrt{q^2+u^2}\right)}, \\ C_s &= -\frac{i\sqrt{1+q^2+u^2} S_v(q, u)}{\pi\sqrt{q^2+u^2} \left(\sqrt{1+q^2+u^2} + \sqrt{q^2+u^2}\right)}. \end{aligned} \quad (14)$$

If $q^2 + u^2 = 0$, then the coefficients C_d^α , C_s in the expansions (8,12) are equal to zero. The function $S_v(q, u)$ is determined by the spatial Fourier spectrum of the magnetic field distribution H_v in the plane $z = 0$:

$$S_v(q, u) = \frac{i}{2} \int_{-\infty}^{+\infty} dx \exp(-iqx) \int_{-\infty}^{+\infty} dy \exp(-iuy) H_v(y, x), \quad (15)$$

Substitution of H_v (6) in the expansion (15) leads to the following representation of the spectral function $S_v(q, u)$:

$$S_v(q, u) = \rho_v \int_0^{+\infty} dy \sin(uy) \begin{cases} I_1(y\sqrt{1+q^2})K_1(\rho_v\sqrt{1+q^2}), & y \leq \rho_v; \\ I_1(\rho_v\sqrt{1+q^2})K_1(y\sqrt{1+q^2}), & y \geq \rho_v. \end{cases} \quad (16)$$

The details of the numerical simulations of the spectral function $S_v(q, u)$ are presented in Appendix A. Using the asymptotic expansion of the modified Bessel functions $I_1(\zeta)$, $K_1(\zeta)$ for $\zeta \gg 1$ one can obtain

$$S_v(q, u) \sim \frac{\sin(u\rho_v)}{u^2}, \quad u \gg 1, \quad u \gg q, \quad (17)$$

which is a good approximation of the exact expression (16) at the large values of spectral variable u . In the other limiting case ($q, u \ll 1$, $u\rho_v \ll 1$) it is convenient to represent the spectral function $S_v(q, u)$ (16) as

$$S_v(q, u) \simeq a u, \quad q, u \ll 1, \quad u\rho_v \ll 1, \quad (18)$$

where the factor a is expressed in terms of the vortex radius ρ_v :

$$a = \rho_v \left[K_1(\rho_v) \int_0^{\rho_v} d\zeta \zeta I_1(\zeta) + I_1(\rho_v) \int_{\rho_v}^{+\infty} d\zeta \zeta K_1(\zeta) \right]. \quad (19)$$

Thus, the magnetic field structure of a solitary vortex half-ring placed near the flat surface of a type-II superconductor is fully determined by the relations (4,6,8,10,12,14,16). The field $\mathbf{H}_d$ describes the disturbances of the structure of the toroidal Abrikosov vortex (6) by the surface S . In the area of the vortex core the field $\mathbf{H}_d$ is in opposite direction to the vortex line, so that $(\mathbf{H}_d \cdot \mathbf{H}_v) < 0$. It results in a decrease of the magnetic field value at the VL. The superconductor surface effect is strong only in the surface layer of a thickness defined by the vortex radius ρ_v or the magnetic field penetration depth λ .

The field $\mathbf{H}_s$ denotes the scattered magnetic field outside the superconductor, produced by the isolated flux line in the form of the half-ring placed near the surface. To determine a structure of the field $\mathbf{H}_s$ let us estimate a behavior of the potential U_s (12) at long distances $z \gg 1, \rho_v$ from the surface. Since the integrand in (12) drops abruptly if $q^2 + u^2 > (1/z)^2$, only small values of the spectral variables q and u are important. Assuming that $q, u \ll 1, 1/\rho_v$ and using the approximate expression of the spectral function $S_v(q, u)$ (18), the potential U_s (12) can be written in the form:

$$U_s \simeq \frac{2a}{\pi^2} \int_0^{+\infty} dq \cos(qx) \int_0^{+\infty} du \frac{u \sin(uy)}{\sqrt{q^2 + u^2}} \exp(-z\sqrt{q^2 + u^2}), \quad z \gg 1, \rho_v. \quad (20)$$

It is shown in Appendix B, that the potential (20) is the potential of the dipole $P = 2\rho_v Q$ (see the inset of fig. 2), if the effective charge $Q = a/2\pi\rho_v$. Figure 2 plots the values of the charge Q and dipole moment P versus the vortex radius ρ_v . The dipole structure of the potential U_s determines the asymptotic decay law for the scattered field $\mathbf{H}_s$ at long distances $z \gg 1, \rho_v$ from the surface: $H_s \sim R^{-3}$, where $R = (x^2 + y^2 + z^2)^{1/2} \gg \rho_v$ is the distance from the center of the vortex half-loop.

To calculate the magnetic flux Φ in an Abrikosov vortex, the cross-section Σ has to be selected perpendicular to the vortex line. In the case of the vortex half-ring the intersection plane Σ has to include the center of the semicircle formed by the VL and the axis x (see fig. 1). The specific feature of magnetic structures in the form of a vortex half-ring is self-consistent localization of both the magnetic field and supercurrent in the vicinity of the VL. Since the magnetic field and the supercurrent vanish at large distances from the VL, the total magnetic flux Φ_Σ across the plane Σ is equal exactly to zero:

$$\Phi_\Sigma = \Phi_{\Sigma_-} + \Phi_{\Sigma_+} \equiv 0, \quad (21)$$

Here $\Phi_{\Sigma_\pm}$ are the magnetic fluxes across the corresponding half-planes $\Sigma_\pm$. Using the Gauss theorem, it is easy to verify that the fluxes $\Phi_{\Sigma_\pm}$ do not depend on the orientation of the intersection plane Σ relative to the surface of the superconductor. So, by choosing

for simplicity the plane $y = 0$ as the cross-section Σ , one can obtain:

$$\Phi_{\Sigma-} = \Phi_v + \Phi_d, \quad (22)$$

$$\begin{aligned} \Phi_v &= \int_{-\infty}^{+\infty} dx \int_{-\infty}^0 dz H_v(z, x), & \Phi_d &= \int_{-\infty}^{+\infty} dx \int_{-\infty}^0 dz H_d^y(x, 0, z), \\ \Phi_{\Sigma+} &\equiv \Phi_s = \int_{-\infty}^{+\infty} dx \int_0^{+\infty} dz H_s^y(x, 0, z). \end{aligned} \quad (23)$$

The term Φ_v is the magnetic flux in the solitary toroidal Abrikosov vortex and was calculated in [11]

$$\Phi_v(\rho_v) = 1 - \rho_v K_1(\rho_v), \quad (24)$$

and the magnetic fluxes Φ_d and Φ_s are determined completely by the spectral function $S_v(q, u)$:

$$\Phi_d = -\frac{2}{\pi} \int_0^{+\infty} du \frac{S_v(0, u)}{u + \sqrt{1 + u^2}}, \quad (25)$$

$$\Phi_s = -\frac{2}{\pi} \int_0^{+\infty} du \frac{\sqrt{1 + u^2} S_v(0, u)}{u (u + \sqrt{1 + u^2})}. \quad (26)$$

Using the relations (24,25,26) and the definition of the spectral function $S_v(q, u)$ (15) it is easy to verify that the total magnetic flux Φ_{Σ} is really equal to zero. The results of the simulations of the magnetic fluxes Φ_v and $\Phi_{\Sigma-}$ versus the vortex radius ρ_v are shown in fig. 3. The magnetic flux $\Phi_{\Sigma-}$ of the vortex half-ring depends strongly on the VL radius ρ_v and tends asymptotically to the quantum of magnetic flux Φ_0 at large values of ρ_v . The flux $\Phi_{\Sigma-}$ differs noticeably from the flux of a toroidal Abrikosov vortex Φ_v . It means that the surface of a superconductor affects significantly the magnetic field structure of

the vortex half-ring, thus largely reducing the value of the magnetic field in the vortex core area [13].

In the region $z \leq 0$, occupied by the superconductor, the London equation (1) implies the following expression for the free energy G_- [9]:

$$G_- = \frac{1}{8\pi} \int_{z=0} dx dy [\mathbf{H} \times \text{rot } \mathbf{H}]_z + \frac{1}{8\pi} \int_{z \leq 0} dV \mathbf{H} (\mathbf{H} + \text{rot rot } \mathbf{H}). \quad (27)$$

The energy contribution of the magnetic field $\mathbf{H}_s$ outside the superconductor ($z > 0$) is defined in the usual way:

$$G_+ = \frac{1}{8\pi} \int_{z > 0} dV (\mathbf{H}_s)^2. \quad (28)$$

The total free energy G_0 is the sum of the expressions (27,28):

$$G_0 = G_- + G_+. \quad (29)$$

To find the free energy of the vortex half-ring it is necessary to substitute the solutions (4,6,8,10,12,14,16) describing the magnetic field distributions $\mathbf{H}$ and $\mathbf{H}_s$ in the expressions (27,28,29). It is convenient to extract the contribution of the superconductor surface and represent the energy G_0 as the sum:

$$G_0 = G_v + G_s. \quad (30)$$

Here the first term G_v is the free energy of the half of the toroidal Abrikosov vortex. The magnitude of G_v is fully determined by the value of the magnetic field in the center of the vortex line [10, 11]:

$$G_v = \frac{\rho_v}{8} H_v(\rho_v, 0). \quad (31)$$

The second term G_s includes the total influence of the surface S and is expressed in terms of the spectral function $S_v(q, u)$:

$$G_s = \frac{\rho_v}{2\pi^3} \int_0^{+\infty} dq \int_0^{+\infty} du \frac{u \sqrt{1+q^2+u^2} S_v(q, u) D(q, u)}{\sqrt{q^2+u^2} \left(\sqrt{1+q^2+u^2} + \sqrt{q^2+u^2} \right)}, \quad (32)$$

$$D(q, u) = \frac{\sin(u\rho_v)}{u\rho_v} - \int_0^{\pi/2} d\varphi \left[\cos \varphi \cos(u\rho_v \sin \varphi) \right. \\ \left. + \frac{q^2+u^2}{u\sqrt{1+q^2+u^2}} \sin \varphi \sin(u\rho_v \sin \varphi) \right] \exp(-\rho_v \cos \varphi \sqrt{1+q^2+u^2}).$$

Expression (6) has a logarithmic divergence at the VL center ($\rho = \rho_v, x = 0$), since the London equation (5) is not valid in the region of the normal vortex core. To compute the energy G_v (31), the magnetic field $H_v(\rho_v, 0)$ was thus truncated at the distance ξ from the VL center. The details of the numerical simulations of the magnetic field $H_v(\rho_v, 0)$ are presented in Appendix C. Figure 4 gives the dependencies of the energies G_v and G_s on the radius of the vortex half-ring ρ_v . Let us note that $G_s \ll G_v$ at any values of the vortex radius. It means that the free energy G_0 is modified insignificantly by the surface of the superconductor and the estimate

$$G_0(\rho_v) \simeq G_v(\rho_v) \quad (33)$$

accurately approximates the exact value of the free energy of the vortex half-ring.

Thus, the free energy $G_0(\rho_v)$ of the Abrikosov vortex in the form of a semicircle of radius ρ_v exceeds very slightly the energy $G_v(\rho_v)$ of half of the toroidal vortex. At the same time, the magnetic field structures of these vortices differ noticeably, especially inside the layer with thickness $\sim \lambda$ near the surface. The surface changes the structure of the toroidal vortex, such that the value of the magnetic field in the core of the vortex decreases. As a consequence, the magnetic fluxes $\Phi_{\Sigma\pm}$ (22,23) of the vortex half-ring are smaller than the magnetic flux Φ_v (24) of the toroidal Abrikosov vortex even if the size of the vortices exceeds the magnetic field penetration depth λ ($\rho_v \gtrsim \lambda$). Due to the

continuity of the magnetic flux, the flux line creates the scattering field $\mathbf{H}_s$ outside the superconductor. The energy of the magnetic field $\mathbf{H}_s$ makes an important contribution to the total free energy of the vortex half-ring and neutralizes the decrease of the London energy G_- (27), forced by the distortions of the vortex structure, induced by the surface of superconductor.

3. VORTEX HALF-RING IN AN APPLIED MAGNETIC FIELD

The behavior of a superconductor in an applied magnetic field $\mathbf{H}_0$ is controlled by the Gibbs free energy [9]:

$$F = G - \frac{1}{4\pi} \int_{z \leq 0} dV (\mathbf{H}\mathbf{H}_0). \quad (34)$$

If the applied field $\mathbf{H}_0$ is directed along the surface S , the magnetic field distribution in the superconductor half-space ($z \leq 0$) (see fig. 1) can be represented as follows:

$$\mathbf{H} = \mathbf{H}_V + \mathbf{H}_m. \quad (35)$$

The first term $\mathbf{H}_V$ obeys equation (1) with the boundary conditions (3) and describes the magnetic field structure of the Abrikosov vortex with arbitrary vortex line, if the applied field is absent. The second term $\mathbf{H}_m = \mathbf{H}_0 \exp(z)$ is the Meissner (vortex-free) distribution of the magnetic field near the surface of the superconductor. The free energy G is defined by the expressions (27,28,29), where the magnetic field $\mathbf{H}$ in the superconductor satisfies relation (35). Taking into account that the field $\mathbf{H}_m$ on the superconductor surface S coincides with the applied magnetic field $\mathbf{H}_0$, the Gibbs free energy F (34) measured relative to the free energy of the Meissner state can be expressed as:

$$F = G_V + \frac{1}{4\pi} \int_{l_v} d\mathbf{l}_v \mathbf{H}_m - \frac{1}{4\pi} \int_{l_v} d\mathbf{l}_v \mathbf{H}_0. \quad (36)$$

Here G_V is the free energy of an Abrikosov vortex described by the term $\mathbf{H}_V$ in (35) in a zero applied magnetic field. The VL location of this vortex in space is determined by arbitrary curve l_v and the vector $d\mathbf{l}_v = dl_v \mathbf{e}_v$ is directed along the vortex line. It should be noted that expression (36) sets the relation between the free energy of the Abrikosov vortex G_V and the Gibbs free energy F for arbitrary shape of the vortex line. Using (36), it is easy to write the Gibbs free energy of the Abrikosov vortex in the form of a semicircle of arbitrary radius ρ_v :

$$F(\rho_v) = G_0(\rho_v) - \frac{H_0 \rho_v}{2\pi} \left[1 - \int_0^{\pi/2} d\varphi \sin \varphi \exp(-\rho_v \sin \varphi) \right]. \quad (37)$$

Figure 5 gives the dependencies of the Gibbs free energy F (37) on the radius of the vortex half-ring ρ_v for some values of an applied magnetic field H_0 . The type of the curve $F(\rho_v)$ depends strongly on the value of the applied magnetic field H_0 . Taking into account the equality (33) and considering that in the case $\rho_v \gg 1$ the following approximate expression for the free energy $G_v(\rho_v)$ holds

$$G_v(\rho_v) \simeq \frac{H_{c1}}{4} \rho_v, \quad \rho_v \gg 1, \quad (38)$$

one can obtain the asymptotic behavior of the Gibbs free energy $F(\rho_v)$ for $\rho_v \gg 1$:

$$F(\rho_v) \simeq \frac{\rho_v}{2\pi} \left[\frac{\pi}{2} H_{c1} - H_0 \right], \quad \rho_v \gg 1. \quad (39)$$

Here $H_{c1} = \ln(\kappa)/4\pi$ is the lower critical magnetic field for the London model. If $H_0 < H_{c1}^* = \pi H_{c1}/2$, the Gibbs free energy $F(\rho_v)$ is positive for any $\rho_v \neq 0$, and the Meissner state has the minimal energy. So, the existence of vortex half-rings in the superconductor is forbidden, and only vortex-free distributions of the magnetic field and supercurrent are possible. In the case of $H_0 = H_{c1}^*$, the Gibbs free energy of a state containing a vortex half-ring of a large radius $\rho_v \gg 1$ matches the energy of the Meissner state. It should be

noted that the vortex half-ring is asymptotically stable in this case, because

$$\lim_{\rho_v \rightarrow \infty} \frac{dF}{d\rho_v} = 0.$$

So, the field H_{c1}^* is the minimal applied magnetic field, when it is energetically favorable for a vortex half-ring to be formed near the flat surface of type-II superconductor. If $H_0 > H_{c1}^*$, there is a critical radius ρ_c of the vortex half-ring at which the curve $F(\rho_v)$ has its maximum U (see the inset in fig. 6). Figure 6 gives the dependencies of the height of the surface energy barrier U and the critical radius ρ_c on the value of an applied magnetic field H_0 . Since the Gibbs free energy $F(\rho_v)$ decreases monotonically at $\rho_v > \rho_c$, the energy barrier U prevents nucleation of expanding vortex loops near the surface. The barrier height U is reduced by increasing the applied field H_0 . When the applied field H_0 is large enough for the critical radius ρ_c to become of the order of the coherence length ξ , the surface barrier U vanishes. Using the approximate expression for the free energy G_v of the vortex half-ring [15, 16]

$$G_v(\rho_v) \simeq \frac{\rho_v}{4} \left[H_{c1} + \frac{\ln(\rho_v)}{4\pi} \right], \quad \rho_v < 1 \quad (40)$$

one can estimate that the surface barrier U is destroyed

$$\frac{dF}{d\rho_v} \simeq \frac{1}{16\pi} - \frac{\rho_v H_0}{4} \leq 0 \quad \text{for} \quad \rho_v = \xi,$$

when the applied magnetic field H_0 becomes of the order of the thermodynamic critical field in the superconductor $H_{cm} = \frac{\kappa}{2\pi\sqrt{2}}$. Thus, the same applied magnetic fields are required to destroy both the surface barrier for a vortex half-ring and the Bean-Livingston barrier for a rectilinear VL parallel to the surface.

4. DISCUSSION OF THE RESULTS

The solutions of the London equations were obtained here to describe the structure of a curved Abrikosov vortex near the flat surface of a type-II superconductor. The VL of such a vortex is a semicircle of arbitrary radius. The interaction of this vortex half-ring

and an applied magnetic field was considered by calculating the Gibbs free energy. This problem extends the well-known ideas concerning the surface Bean–Livingston barrier [4], for the case where the Abrikosov vortex is curved. Vortex loops like these represent an example of compact magnetic structures in SC [17]. The specific feature of such magnetic structures is the self-consistent localization of both the supercurrent and the magnetic field in all three dimensions. Due to the continuity of the magnetic flux, the end points of the vortex loop touch the surface of SC, and the vortex line produces a scattered field $\mathbf{H}_s$ outside the superconductor. The creation of the vortex loops is depressed significantly by the surface energy barrier. The height of this barrier is reduced by increasing of the applied magnetic field H_0 . The surface barrier disappears completely when the field H_0 becomes of the order of the thermodynamic critical field H_{cm} , and the deterministic nucleation of small vortex loops with size comparable to the coherence length ξ is possible. The applied magnetic field $\mathbf{H}_0$ produces the Meissner supercurrent

$$\mathbf{j}_m = \frac{1}{4\pi} \text{rot } \mathbf{H}_m, \quad (41)$$

distributed mainly in the layer of thickness λ near the surface. At the surface the density of the Meissner current, corresponding to the applied field $H_0 = H_{cm}$, is comparable to the depairing current density $j_c = \frac{\kappa}{12\sqrt{3}\pi^2}$ [9]. Since the inhomogeneity of the Meissner current density is not important at scales of the coherence length ξ , the condition $j_m \sim j_c$ determines the threshold of thermodynamic stability of the uniform current carrying state in superconductors [6, 9] and agrees with the Landau criterion of roton excitation in a superfluid flow [15, 18].

At a nonzero temperature T , before the surface barrier is destroyed ($H_0 < H_{cm}$), the penetration of magnetic flux into the SC occurs due to thermally activated nucleation, subsequent growth, and merging of vortex half-rings. A similar mechanism of thermally assisted overcoming of energy barriers should be important at high temperatures T near T_c [19] especially in materials with strong thermal fluctuations [14, 20].

The creation of expanding vortex loops near a superconductor surface is similar to the generation of closed Abrikosov vortices by an external current [14, 15]. Since the

energy of the vortex half-ring G_v (31) grows monotonically with the radius of the VL ρ_v , the nucleation and expansion of vortex loops results in the increase of the total free energy of superconductor. The decrease of the Gibbs free energy F (37) is determined by the work $\Delta W(\rho_v)$, performed by the source of the applied magnetic field $\mathbf{H}_0$ during the expansion of the vortex loop up to size ρ_v :

$$\Delta W(\rho_v) = \frac{H_0 \rho_v}{2\pi} \left[1 - \int_0^{\pi/2} d\varphi \sin \varphi \exp(-\rho_v \sin \varphi) \right]. \quad (42)$$

The work $\Delta W(\rho_v)$ is related to the motion of the vortex line under the action of the Lorentz force f_L [21]

$$\mathbf{f}_L = [\mathbf{j}_m \times \mathbf{e}_v] \quad (43)$$

caused by the Meissner current $\mathbf{j}_m$. Since the current $\mathbf{j}_m$ decreases outside a surface layer of thickness $\sim \lambda$, the interaction of the applied magnetic field and the vortex half-ring depends strongly on the size of the vortex ρ_v . If $\rho_v \ll 1$, the vortex line is located wholly in the area where the current density $\mathbf{j}_m$ is distributed uniformly, and $\Delta W \sim \rho_v^2$ [14, 15, 16]. In the other limiting case ($\rho_v \gg 1$), the integrand in the expression (42) drops abruptly if $\sin \varphi \sim 1$, and the region $\sin \varphi \lesssim 1/\rho_v \ll 1$ makes an essential contribution to the integral in (42). Replacing $\sin \varphi \simeq \varphi$ in (42) it is easy to obtain

$$\Delta W(\rho_v) \simeq \frac{H_0 \rho_v}{2\pi} \quad \text{for } \rho_v \gg 1.$$

In this case the basic part of the vortex line is located outside the surface layer of a thickness $\sim \lambda$, where the Meissner current $\mathbf{j}_m$ is absent, and the work δW is produced by the motion of parts of the VL, that border on the surface.

The equilibrium shape of the Abrikosov vortex is determined mainly by the structure of the applied magnetic field and represents a rectilinear VL parallel to the surface. The semicircle is the correct form of a vortex nucleus near the surface of the superconductor only if the vortex radius $\rho_v \ll 1$. In this case the Meissner current $\mathbf{j}_m$ does not change essentially on scales of the size of the vortex, so the value of the Lorentz force f_L (43) is

the same for different points of the vortex line. Thus an expansion of the vortex half-ring takes place without distortions of the form of the vortex line. When the size of the vortex ρ_v becomes comparable to the magnetic field penetration depth λ ($\rho_v \gtrsim \lambda$), the value of the Lorentz force f_L reduces strongly for the parts of the vortex line, placed farther from the surface. It results in distortions of the form of the vortex line so that vortex loops elongate parallel to the surface. It is evident that the vortex line of such an elongated vortex loop has a large part directed along the applied magnetic field.

The pattern of expanding single vortex half-rings holds as long as the radius of the vortex ρ_v is much smaller than the typical intervortex distance L . If the intervortex distance becomes comparable with the sizes of the vortex, the regular expansion of vortex half-ring is changed by the interaction of adjacent vortices. The attraction of the sections of the vortices of opposite directions may lead to intersection and cross joining of the adjacent vortices [3]. Figure 7 shows the sequence of formation of a rectilinear Abrikosov vortex parallel to the surface by joining of expanding vortex loops. It is essential, that if the applied magnetic field is not enough to destroy the surface barrier ($H_0 < H_{cm}$), and the thermally activated motion of vortices over the barrier takes place, the creation of a rectilinear Abrikosov vortex near the surface by intersection and joining of the vortex loops can allow for the magnetic field entry in type-II superconductor. The surface barrier in this case is determined by the energy barrier U preventing generation of a single vortex half-ring and may be lower than the ordinary BL barrier for a rectilinear Abrikosov vortex [4]. The adjacent vortex loops, which penetrate after the first one, require less energy than U [19]. Therefore, the process of the formation of a rectilinear Abrikosov vortex is of avalanche-type, and U is the activation barrier for the vortex entry [22].

5. CONCLUSION

In this paper the properties of the Abrikosov vortex in the form of a semicircle of arbitrary radius ρ_v near the flat surface of type-II superconductor in the applied magnetic field $\mathbf{H}_0$, parallel to the surface, have been theoretically studied. The magnetic field structure, the magnetic flux and the free energy of a vortex half-ring have been calculated

in the London approximation. The creation of such vortices is delayed by the surface barrier, similar to the Bean–Livingston barrier for a rectilinear Abrikosov vortex [4]. The barrier is reduced by increasing the applied magnetic field H_0 and vanishes in the thermodynamic critical field H_{cm} , so that the deterministic nucleation of vortex loops with the size of coherence length ξ becomes possible. At temperatures T near T_c and for applied fields $H_0 < H_{cm}$ the magnetic flux penetrates into a type-II superconductor by thermally activated nucleation of expanding vortex half-rings near the surface. The formation of the rectilinear Abrikosov vortices by intersection and cross joining of vortex loops has been considered.

APPENDIX A

Let us express the spectral function $S_v(q, u)$ by means of the auxiliary function $w_{qu}(z)$, satisfying the following inhomogeneous differential equation with the zero initial conditions:

$$\begin{aligned} w_{qu}'' - \frac{1}{z} w_{qu}' - (1 + q^2) w_{qu} &= -\sin(uz), \\ w_{qu}(0) = w_{qu}'(0) &= 0. \end{aligned} \tag{A.1}$$

Writing the Green function for equation (A.1), one can obtain the particular solution:

$$\begin{aligned} w_{qu}(z) &= z K_1(z\sqrt{1+q^2}) \int_0^z d\zeta \sin(u\zeta) I_1(\zeta\sqrt{1+q^2}) \\ &\quad - z I_1(z\sqrt{1+q^2}) \int_0^z d\zeta \sin(u\zeta) K_1(\zeta\sqrt{1+q^2}). \end{aligned}$$

Using the known integral:

$$\int_0^{+\infty} d\zeta K_1(a\zeta) \sin(u\zeta) = \frac{\pi u}{2a\sqrt{a^2 + u^2}},$$

one can set the following relation between the functions $S_v(q, u)$ and $w_{qu}(z)$:

$$S_v(q, u) = w_{qu}(\rho_v) + \frac{\pi u \rho_v I_1(\rho_v \sqrt{1+q^2})}{2\sqrt{1+q^2} \sqrt{1+q^2 + u^2}}. \tag{A.2}$$

Thus, to simulate the value of the function $S_v(q, u)$ for arbitrary q and u it is possible to solve the equation (A.1) on the interval $z \in [0, \rho_v]$ and to substitute the obtained value $w_{qu}(\rho_v)$ in expression (A.2). This method of calculation of the spectral function $S_v(q, u)$ is especially efficient for large values $q, u \gg 1$, because it uses the well-known algorithms of solution of Cauchy problem instead of simulations of improper integrals on rapidly oscillating functions.

APPENDIX B

The potential U_P of the dipole $P = 2\rho_v Q$ placed in the plane $z = 0$ as shown in the insert of fig. 2 is described by the well known expression [23]:

$$U_P = P \frac{y}{R^3}, \quad R = (x^2 + y^2 + z^2)^{1/2} \gg \rho_v. \quad (\text{B.1})$$

Let us represent the potential U_P in the form of the two dimensional Fourier transform over spatial harmonics:

$$U_P = \frac{1}{2\pi} \int_{-\infty}^{+\infty} dq \exp(iqx) \int_{-\infty}^{+\infty} du \exp(iuy) S_P(q, u, z). \quad (\text{B.2})$$

The spatial spectrum S_P obeys the inverse Fourier transform and should be written as follows:

$$S_P = \frac{1}{2\pi} \int_{-\infty}^{+\infty} dx \exp(-iqx) \int_{-\infty}^{+\infty} dy \exp(-iuy) U_P(x, y, z). \quad (\text{B.3})$$

Substitution of U_P (B.1) in the expansion (B.3) leads to the following expression of the spectrum S_P :

$$S_P = -\frac{2iP}{\pi} u \int_0^{+\infty} d\zeta \cos(u\zeta) K_0(q \sqrt{z^2 + \zeta^2}), \quad (\text{B.4})$$

where $K_0(\zeta)$ is the McDonald function. Using the known integral:

$$\int_0^{+\infty} d\zeta \cos(u\zeta) K_0(q \sqrt{z^2 + \zeta^2}) = \frac{\pi \exp(-z \sqrt{q^2 + u^2})}{2 \sqrt{q^2 + u^2}}$$

one can obtain:

$$S_P(q, u, z) = -iP \frac{u \exp(-z \sqrt{q^2 + u^2})}{\sqrt{q^2 + u^2}}. \quad (\text{B.5})$$

Thus, the potential U_P of the dipole P at long distances $R \gg \rho_v$ is determined by the expression:

$$U_P = \frac{2P}{\pi} \int_0^{+\infty} dq \cos(qx) \int_0^{+\infty} du \frac{u \sin(uy)}{\sqrt{q^2 + u^2}} \exp(-z \sqrt{q^2 + u^2}). \quad (\text{B.6})$$

APPENDIX C

To compute the magnetic field value at the vortex line center, we use the other representation of the magnetic field distribution $H_v(\rho, x)$ in a toroidal Abrikosov vortex [10]:

$$H_v(\rho, x) = \frac{\rho_v}{2} \int_0^{+\infty} dq \frac{q J_1(q\rho) J_1(q\rho_v) \exp(-|x| \sqrt{1+q^2})}{\sqrt{1+q^2}}, \quad (\text{C.1})$$

where $J_1(\zeta)$ is the Bessel function of the first kind. It is easy to verify, that expression (C.1) is the exact solution of equation (5). The integral in (C.1) is divergent for $\rho = \rho_v$, $x = 0$, because of the integrand function falls down too slowly. To estimate the magnetic field value $H_v(\rho_v, 0)$ let us extract the divergent part of integrand function

$$S_h(q, \rho) = \frac{q J_1(\rho q) J_1(\rho_v q)}{\sqrt{1+q^2}}.$$

Using the asymptotic expansion of the Bessel function $J_1(\zeta)$ for $\zeta \gg 1$, one can obtain the following behavior of the function $S_h(q, \rho)$:

$$S_h(q, \rho) \simeq \frac{\cos[q(\rho - \rho_v)]}{\pi \rho_v \sqrt{1+q^2}} - \frac{\sin(2q\rho_v)}{\pi q \rho_v} \quad \text{for } q \gg \max(1, 1/\rho_v, 1/\rho). \quad (\text{C.2})$$

The first term in (C.2) results in the logarithmic divergence of expression (C.1) if $\rho \rightarrow \rho_v$, $x \rightarrow 0$, because of

$$\int_0^{+\infty} dq \frac{\cos[q(\rho - \rho_v)]}{\sqrt{1+q^2}} = K_0(|\rho - \rho_v|), \quad (\text{C.3})$$

where $K_0(\zeta)$ is the McDonald function. The value of the last integral have to be truncated in the usual way at the distance ξ from the VL center by setting $|\rho - \rho_v| = \xi$ in (C.3), so that the following representation of the magnetic field value $H_v(\rho_v, 0)$ at the VL center holds:

$$H_v(\rho_v, 0) = \frac{K_0(\xi) - \pi/2}{2\pi} + \frac{\rho_v}{2} \int_0^{+\infty} dq \left[\frac{q J_1^2(q\rho_v)}{\sqrt{1+q^2}} - \frac{1}{\pi \rho_v \sqrt{1+q^2}} + \frac{\sin(2q\rho_v)}{\pi q \rho_v} \right]. \quad (\text{C.4})$$

The new integrand function in (C.4) falls down quickly enough to provide the convergence of the improper integral in expression (C.4).

REFERENCES

- [1] A. A. Abrikosov, Zh. Eksp. Teor. Fiz. **32** (1957) 1442; Sov. Phys. JETP **5** (1957) 1174.
- [2] R. P. Huebener, Magnetic Flux Structures in Superconductors, (Springer-Verlag, Berlin, 1979).
- [3] A. M. Campbell and J.E. Evetts, Critical Currents in Superconductors, (Barnes & Noble, New-York, 1972).
- [4] C. P. Bean and J. D. Livingston, Phys. Rev. Lett. **12** (1964) 14.
- [5] J. R. Clem, R. P. Huebener and D. E. Gallus, J. Low Temp. Phys. **12** (1973) 449.
- [6] V. P. Galaiko, Zh. Eksp. Teor. Fiz. **50** (1966) 1322; Sov. Phys. JETP **23** (1966) 1202.
- [7] B. V. Petukhov and V. R. Chechiotkin Zh. Eksp. Teor. Fiz. **65** (1973) 1653; Sov. Phys. JETP **38** (1974) 827.
- [8] A. E. Koshelev, Physica C **191** (1992) 219.
- [9] A. A. Abrikosov, Fundamentals of the Theory of Metals, (North-Holland, Amsterdam, 1988).
- [10] V. A. Kozlov and A. V. Samokhvalov, Pis'ma Zh. Eksp. Teor. Fiz. **53** (1991) 150; JETP Lett. **53** (1991) 158.
- [11] V. A. Kozlov and A. V. Samokhvalov, Physica C **213** (1993) 103.
- [12] Y. A. Genenko, Phys. Rev. B **49** (1994) 6950.
- [13] O. Fritz, M. Wülfert, H. J. Hug, H. Thomas, and H.-J. Güntherodt, Phys. Rev. B **47** (1993) 384.
- [14] D. S. Fisher, M. P. A. Fisher, D. Huse, Phys. Rev. B **43** (1991) 130.
- [15] E. B. Kolomeisky, Zh. Eksp. Teor. Fiz. **100** (1991) 301.

- [16] S. Q. Chen, W. J. Skocpol, and E. DeObaldia, M. O'Malley, P. M. Mankiewicz, Phys. Rev. B **47** (1993) 2936.
- [17] G. A. Williams, Physica B **194-195** (1994) 1415.
- [18] R. P. Feynman, Statistical Mechanics (A Set of Lectures), (W. A. Benjamin, Inc., Massachusetts, 1972).
- [19] L. Burlachkov, V B Geshkenbein, A. E. Koshelev, A. E. Larkin, V. M. Vinokur, Phys. Rev. B **50** (1994) 16770.
- [20] D. R. Nelson and H. S. Seung, Phys. Rev. B **39** (1989) 9153.
- [21] V. V. Shmidt, G. S. Mkrtchian, Usp. Fiz. Nauk **112** (1974) 459.
- [22] R. G. Mints and I. B. Snapiro, Phys. Rev. B **47** (1993) 3273.
- [23] L .D. Landau and E .M. Lifshitz, The Classical Theory of Fields (Nauka, Moscow, 1988).

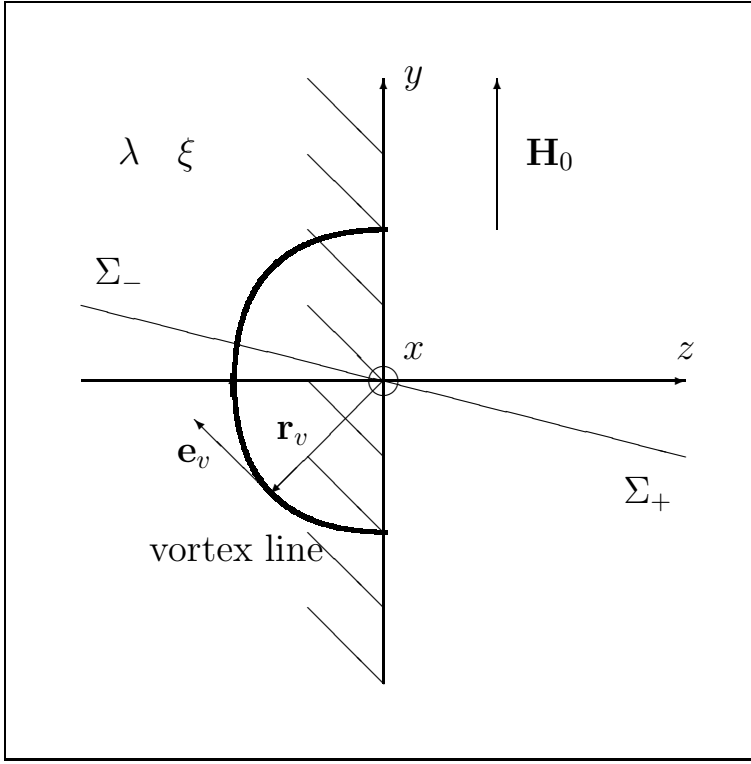


Figure 1: Abrikosov vortex in the form of the semicircle of the radius ρ_v near the flat surface S of type-II superconductor. The superconductor occupies the half-space $z \leq 0$ and is characterized by the magnetic field penetration depth λ and coherence length ξ ; the vortex line is placed in the plane (yz) . The intersection of vortex plane and cross-section $\Sigma = \Sigma_- + \Sigma_+$ is shown.

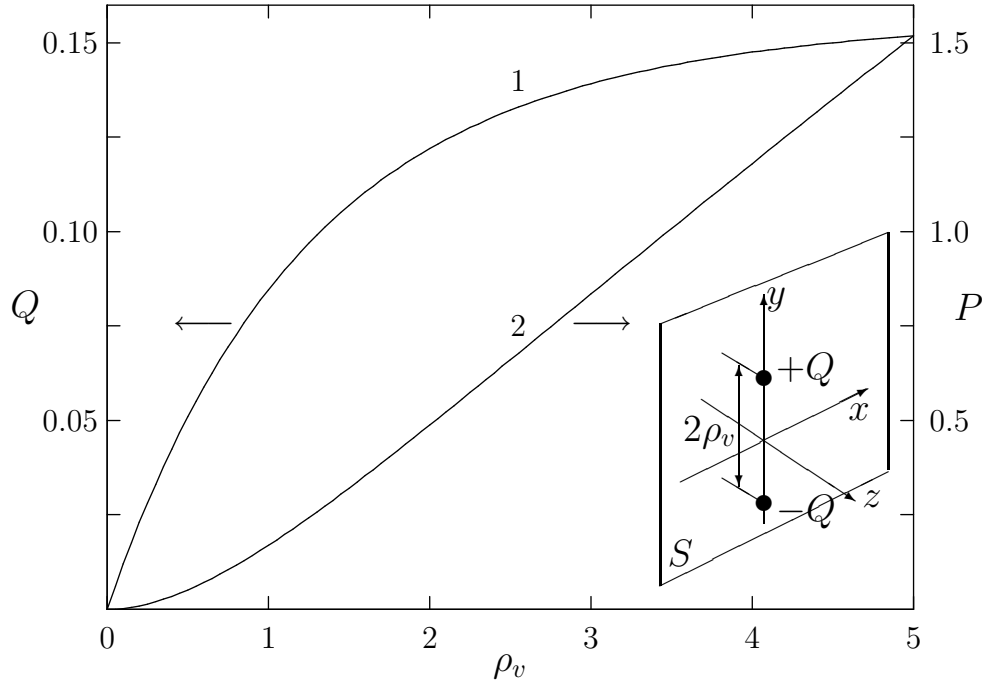


Figure 2: Effective charge Q (1) and dipole moment $P = 2\rho_v Q$ (2) vs. radius of the vortex line ρ_v . The inset shows the dipole P placed in the plane $z = 0$.

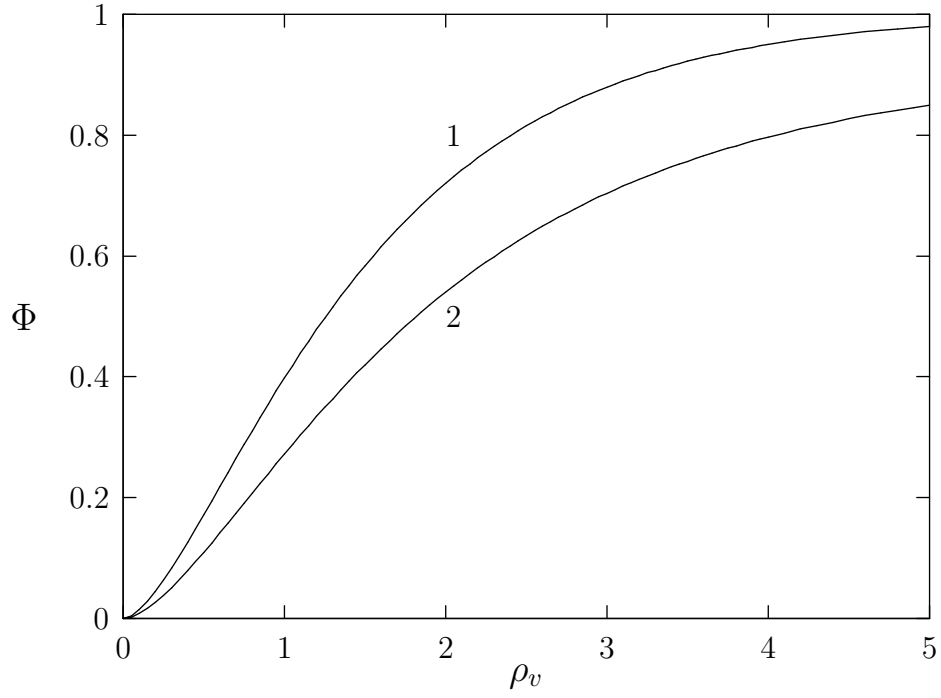


Figure 3: Magnetic flux Φ_v of toroidal Abrikosov vortex (1) and magnetic flux $\Phi_{\Sigma-}$ of the vortex half-ring (2) vs. radius of the vortex line ρ_v .

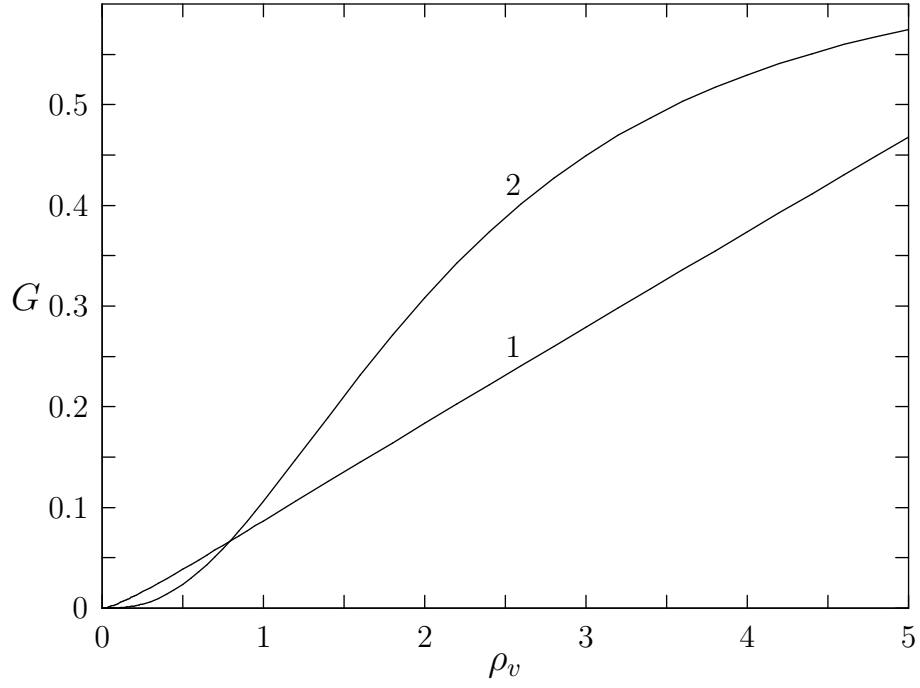


Figure 4: Free energy of half of toroidal Abrikosov vortex G_v (1) and the contribution G_s of the surface of superconductor S to the free energy of the vortex half-ring (2) vs. the radius of the vortex line ρ_v ($\kappa = 100$). To maintain the scale of the vertical axis fixed, the value $100 \cdot G_s$ is used .

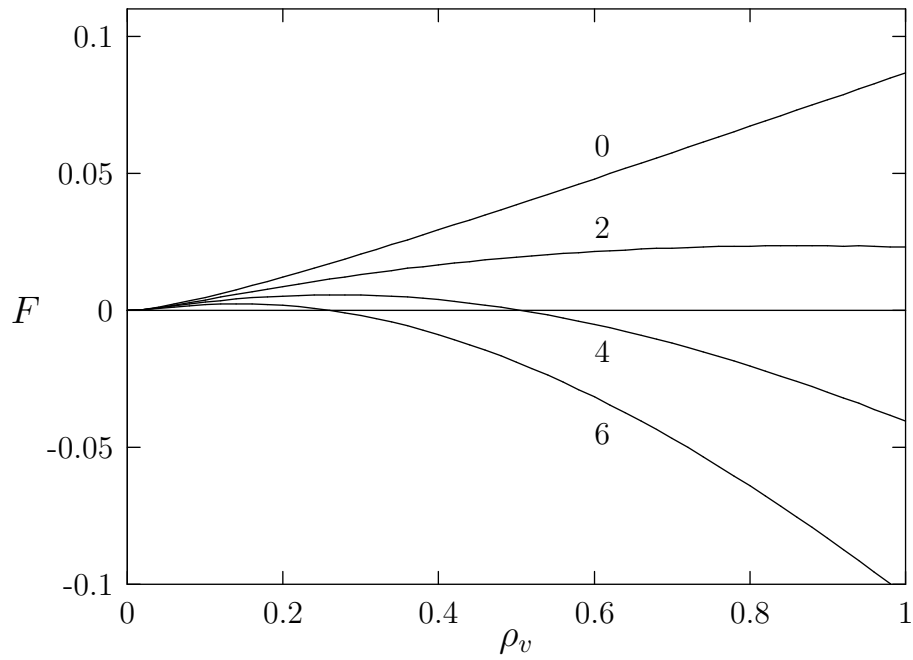


Figure 5: Gibbs free energy F of the vortex half-ring vs. the radius of the vortex line ρ_v for several values of an applied magnetic field H_0 ($\kappa = 100$). The numbers near the curves denote the value of the field H_0 in the units of the lower critical field H_{c1} .

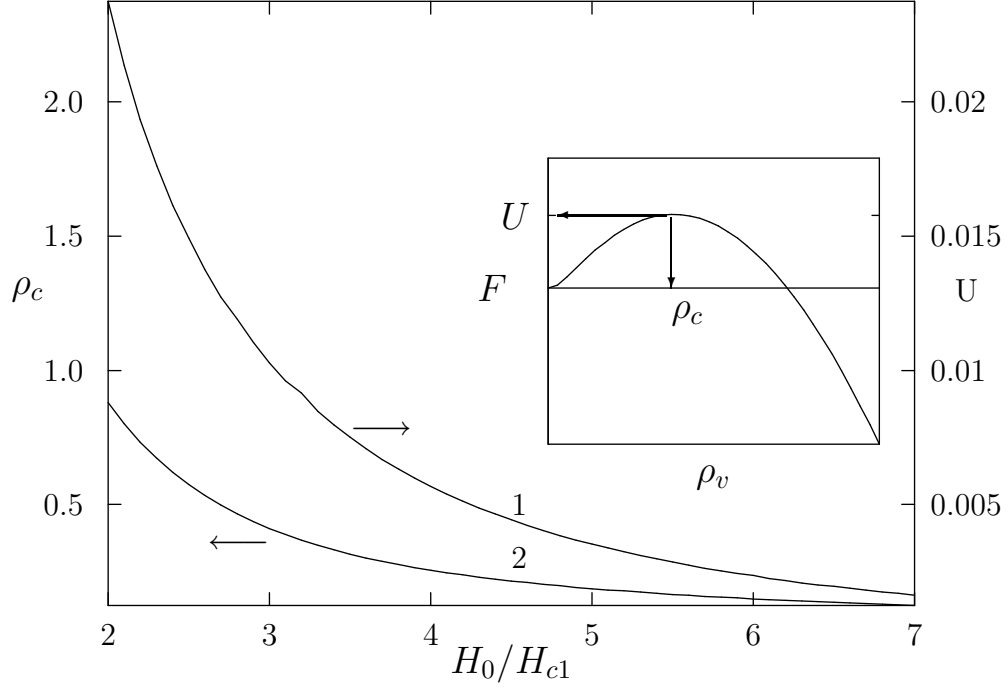


Figure 6: Surface barrier U (1) and critical radius of the vortex half-ring ρ_c (2) vs. the value of the applied magnetic field H_0 ($\kappa = 100$). The inset sketches the part of the curve $F(\rho_v)$. The Gibbs free energy $F(\rho_v)$ has its maximum U at the critical radius ρ_c : $F(\rho_c) = U$.

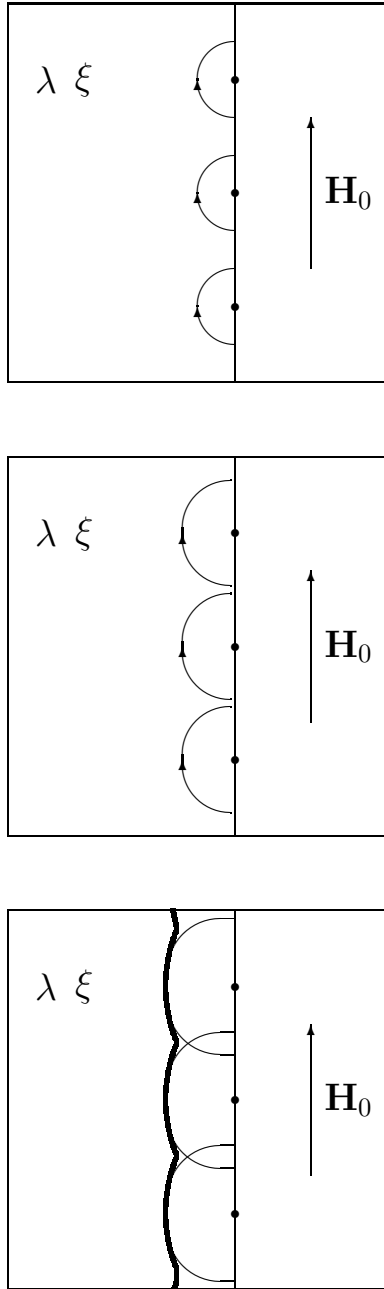


Figure 7: The formation of the rectilinear Abrikosov vortex, parallel to the surface, by intersection and cross joining vortex loops.